

REPORT NO. RL-TR-71-5

SPECIFIC PERMEABILITY OF EPOXY RESIN SYSTEMS

by

James L. Parham

14 June 1971

DTIC QUALITY INSPECTED 2

DISTRIBUTION STATEMENT A

Approved for public release;  
Distribution Unlimited



U.S. ARMY MISSILE COMMAND

Redstone Arsenal, Alabama

19960313 132

ASTEC/4779


#### DISPOSITION INSTRUCTIONS

Destroy this report when it is no longer needed. Do not return it to the originator.

#### DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

# DISCLAIMER NOTICE

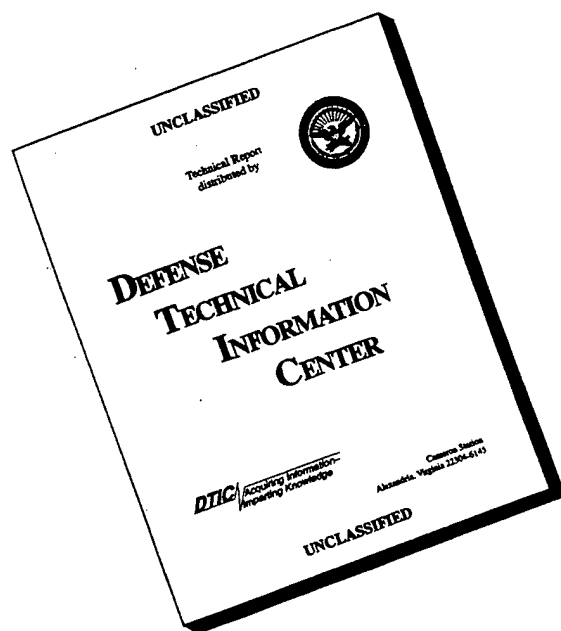

**THIS DOCUMENT IS BEST  
QUALITY AVAILABLE. THE  
COPY FURNISHED TO DTIC  
CONTAINED A SIGNIFICANT  
NUMBER OF PAGES WHICH DO  
NOT REPRODUCE LEGIBLY.**

14 June 1971

Report No. RL-TR-71-5

SPECIFIC PERMEABILITY OF EPOXY RESIN SYSTEMS

by

James L. Parham

DA Project No. 1T062105A329  
AMC Management Structure Code No. 502E.11.29500

Materials Engineering & Development Function  
Ground Equipment & Materials Directorate  
Research, Development, Engineering & Missile Systems Laboratory  
U. S. Army Missile Command  
Redstone Arsenal, Alabama 35809

## ABSTRACT

Several types of coatings and filler materials were evaluated for their effectiveness in reducing moisture permeability of epoxy resins. Only the metallic coatings gave significant reductions. The specific permeability of a number of epoxy resin systems is given at room temperature and 140°F. Data is presented on the effects of post cure, curing agent concentration, and specimen thickness on specific permeability.

## CONTENTS

	Page
1. Introduction .....	1
2. Experimental Methods .....	1
3. Discussion of Results .....	3
4. Conculsions .....	5

## ILLUSTRATIONS

### Figure

1	Payne Permeability Cup .....	7
2	Specific Permeability Versus Curing Agent Concentration .....	8
3	Specific Permeability Versus Thickness ....	9
4	Specific Permeability Versus Post Cure ....	10
5	Specific Permeability Versus Post Cure ....	11

### Table

I	Data on Curing Agents Used in the Tests ...	12
II	Specific Permeability of Various Epoxy Resin Resin Systems .....	13
III	Specific Permeability of An Epoxy Resin System Having Various Coatings and Fillers .	14

REFERENCES .....	15
------------------	----

RETRIEVAL TERMS ASSIGNED BY DDC:

UNCLASSIFIED

RETRIEVAL TERMS ASSIGNED BY DDC: (U) WEIGHT; (U) REDUCTION; (U) \*COMPOSITE MATERIALS; (U) VAPORS; (U) \*EPOXY PLASTICS; (U) \*GUIDED MISSILES; (U) GLASS TEXTILES; (U) MOISTUREPROOFING (U) FILMS; (U) FILLING; (U) ADDITIVES; (U) HUMIDITY; (U) TEMPERATURE; (U) PERMEABILITY; (U)

## RESEARCH AND TECHNOLOGY WORK UNIT SUMMARY

[illegible]

1. TITLE (Precede with Security Classification Code): (U) INVESTIGATION OF LOW-WATER-VAPOR-PERMEABLE RESINS FOR LIGHTWEIGHT COMPOSITE MISSILE STRUCTURES

## 12. SCIENTIFIC AND TECHNOLOGICAL AREAS:

004100 COMP MAT

13. START DATE	14. ESTIMATED COMPLETION DATE	15. FUNDING AGENCY		16. PERFORMANCE METHOD
OCT. 69	CONT.	DA		C. IN-HOUSE
17. CONTRACT/GRANT		18. RESOURCES ESTIMATE	19. PROFESSIONAL MAN YRS	20. FININGS (In thousands)

a. DATES/EFFECTIVE:	EXPIRATION:		
b. NUMBER: *			
c. TYPE: *			
d. AMOUNT:			
e. KIND OF AWARD	F. CUM/TOT:	€ 0	
19. RESPONSIBLE BODY ORGANIZATION		400466	0108
20. PERFORMING ORGANIZATION		400466	0108

ADDRESS: REDSTONE AR AL 01 05 32909

ADDRESS: \* REEDSTONE AL 35809

PRINCIPAL INVESTIGATOR (Furnish SSAN if U.S. Academic Institution)

RESPONSIBLE INDIVIDUAL

NAME: WHEELAHAN, E J

TELEPHONE: 2058761211

## 21. GENERAL USE

21A.

5

2

22. KEYWORDS (Precede EACI with Security Classification Code)

(U) COMPOSITES ; (U) PLASTICS ; (U) PERMEABLE RESINS ; (U) EPOXY RESINS :

23. TECHNICAL OBJECTIVE: 24. APPROACH, 25. PROGRESS (Furnish individual paragraphs identified by number. Precede text of each with Security Classification Code.)

OBJECTIVE: (U) TO INVESTIGATE THE MOISTURE PERMEABILITY PROPERTIES OF EPOXY RESIN SYSTEMS USED IN ARMY MISSILES AND TO DISCOVER MEANS TO PREVENT OR REDUCE SUCH MOISTURE PERMEABILITY. MOISTURE HAS PROVED TO BE EXTREMELY DETRIMENTAL TO THE GLASS FIBERS, WHICH IN CONJUNCTION WITH THE EPOXY RESINS, FORM RIGID COMPOSITE STRUCTURES.

APPROACH: (U) THE PAYNE PERMEABILITY CUP WILL BE USED TO MEASURE MOISTURE PERMEABILITY OF THIN FILMS OF SEVERAL RESIN SYSTEMS AT ROOM AND ELEVATED (TO 160 DEGREES F.) TEMPERATURES. THE EFFECT OF VARIOUS FILLERS, ADDITIVES, AND PROTECTIVE COATINGS ON THE MOISTURE PERMEABILITY WILL BE EVALUATED. SOME OF THE MORE PROMISING TREATMENTS WILL BE USED IN FABRICATING COMPOSITE MATERIALS. THESE COMPOSITES WILL BE EVALUATED UNDER CONDITIONS OF HIGH

APPROACH: (U) THE PAYNE PERMEABILITY CUP WILL BE USED TO MEASURE MOISTURE PERMEABILITY OF THIN FILMS OF SEVERAL RESIN SYSTEMS AT ROOM AND ELEVATED (TO 160 DEGREES F.) TEMPERATURES. THE EFFECT OF VARIOUS FILLERS, ADDITIVES, AND PROTECTIVE COATINGS ON THE MOISTURE PERMEABILITY WILL BE EVALUATED. SOME OF THE MORE PROMISING TREATMENTS WILL BE USED IN FABRICATING COMPOSITE MATERIALS. THESE COMPOSITES WILL BE EVALUATED UNDER CONDITIONS OF HIGH RELATIVE HUMIDITY AND ELEVATED TEMPERATURE.

PROGRESS: (U) 69 10-70 02 - PERMEABILITY TESTS HAVE BEEN PERFORMED ON EPOXY RESINS FILLED WITH A VARIETY OF ORGANIC AND INORGANIC FILLERS. THESE FILLERS INCLUDE KAOLIN, CALCIUM CARBONATE, ALUMINA, AND DOW CORNING Z-6040 SILANE COUPLING AGENT. NO REDUCTION IN SPECIFIC PERMEABILITY DUE TO THE FILLERS WAS OBSERVED. PERMEABILITY TESTS HAVE ALSO BEEN PERFORMED ON RESIN SPECIMENS HAVING METALLIC COATINGS. THE RESIN SURFACE IS SENSITIZED IN SOLUTIONS OF STANNOUS CHLORIDE AND PALLADIUM CHLORIDE. THE METAL PLATE, EITHER COPPER OR NICKEL, IS FORMED IN AN ELECTROLESS PLATING BATH. VERY THIN METALLIC COATINGS OF NICKEL OR COPPER HAVE VERY LITTLE EFFECT ON PERMEABILITY, BUT COATINGS OVER .0001 INCH HAVE SHOWN SIGNIFICANT REDUCTION.

DEF. STAFF OFFICE  
LASTICS TECHNICAL EVALUATION CENTER  
PICATINNY ARSENAL, DOVER, N. J.

\* Available to contractors upon originator's approval.

DD FORM 1 MAY 68 1498m

PROCESSING DATE. 21 APR 68

PAGE 32

UNCLASSIFIED

CLASSIFIED 14779 83

(2)



## 1. INTRODUCTION:

It has been well established that fiberglass composites are highly susceptible to environmental degradation. In fact, severe degradation has been observed in composites exposed to high relative humidity conditions at moderate temperatures. Many observers believe this degradation is caused by entrance of moisture and subsequent corrosion of the reinforcement and degradation of the glass-resin interfacial bond. This moisture may enter through cracks or pinholes in the resin and diffuse through the resin and penetrate the interface between resin and glass.

Various techniques have been tried in efforts to inhibit this degradation from moisture. These include the utilization of glass coupling agents to lessen the bonds' susceptibility to degradation, the selection of low-permeability binder systems and fillers, and the use of coatings as barrier materials to prevent entrance of moisture into the composite. Unfortunately, no detailed study has been made of the effectiveness of many of these processes and treatments.

In the study reported here, an attempt was made to measure the effectiveness of several types of barrier materials and to study several variables affecting moisture transmission through the epoxy resin. These include curing agent concentration, post cure, and temperature.

## 2. EXPERIMENTAL METHODS:

### a. Resin Systems

The epoxy resin used in this study was a standard commercial resin composed of a diglycidyl ether of bisphenol A of molecular weight approximately 380. The curing agents used in these tests were representative of several different types. They are described in Table I.

### b. Test Methods

In this study, moisture transmission was measured by the rate of weight loss from a Payne permeability cup (Figure 1). This cup is a small, hemispherical cup over which a diaphragm of the test material is tightly clamped. Water is placed in the cup and the test specimen clamped and sealed on the cup. The cup is weighed and placed in a desiccator. Subsequent weighings determine weight loss, reflecting moisture transmission through the resin.

In order to compare results from specimens of different thicknesses, all raw data was reduced to transmission of a one-square-centimeter by one-millimeter-thick sample in a 24-hour period. Data in this form is called specific permeability and is expressed in milligrams of water loss per square centimeter of exposed area per millimeter of specimen thickness per 24 hours ( $\text{Mg}/\text{Cm}^2/\text{MM}/24 \text{ hrs}$ ).

The test specimens, except where intentionally varied, averaged about 0.010 inch thick with a range of 0.007 to 0.015 inch. Such variations were caused by different resin viscosities and cure rates.

Preliminary tests indicated that the daily rate of moisture transmission by the specimens varied considerably. This is believed to be caused by several factors. For example, changes in atmospheric pressure and laboratory temperature fluctuations probably caused most of the inconsistencies. Other influences include the minor variations in resin composition and their post cure. To lessen the impact of these variables, measurements of moisture transmission were carried out over a two- or three-week period to average out daily variations. A control was also included with each set of tests.

#### c. Formation of Metallic Coating

The metallic coatings on the resin specimens were applied in three ways; vapor deposition, electroless plating, and electroplating.

In the first method, as recommended for metallized coatings, a baking varnish base was first applied to the resin specimens and cured. The varnished specimens were then placed in a vacuum metallizing chamber and the appropriate metal vaporized to form the coating on the specimens. A thin topcoat of the varnish was then applied to the thin metal coating.

For electroless plating, the resin specimens were first mechanically roughened with sandpaper. The specimens were then sensitized in solutions of stannous chloride and palladium chloride. Immediately after sensitizing, the specimens were transferred to an electroless plating bath where the plating proceeded spontaneously. Specimens were removed from the bath after the desired metal thickness was obtained.

For electroplating, a thin electroless copper flash was first applied to the specimens. Plating of the appropriate metal then proceeded according to standard electroplating methods.

### 3. DISCUSSION OF RESULTS:

#### a. Effect of Various Curing Agents on Specific Permeability

As Table II shows, the type of curing agent used has an important effect on the specific permeability of the resin. The aromatic types had relatively low transmission rates, the anhydrides had high rates, and the aliphatic types varied from high to low.

Unfortunately, no obviously direct relationship can be shown between specific permeability at room temperature and the environmental degradation rates of composites composed of these same resin systems. Degradation rates of these composites are given in references 1 and 2. The aromatic polyamines, a popular type of curing agent for resins used in composites, exhibited low specific permeability and were relatively resistant to environmental degradation. The aliphatic polyamines and polyamides, on the other hand, varied from high to low specific permeability but are all highly susceptible to degradation.

It can also be seen from the table that temperature has a distinct effect on specific permeability. At 140°F, the specific permeabilities of the resins were 10 to 20 times the permeability at room temperature. This may be one cause of the large increase in moisture-induced degradation of composites as the temperature is raised above room temperature. In fact, at the higher temperature, there is some reordering of the position of some of the resins in the table, which more closely correspond to the relative degradation rates of the composites. However, there are still too many variations between the two to declare a definite relationship.

Although the data is inconclusive, it is almost certain that moisture permeability plays an important role in composite degradation. Without permeability in some form or other there could be no moisture degradation of the interface or the reinforcement. The problem is to determine if the small differences in resin permeability account for the differences in rates of degradation of the composites. The data indicates a possible relation between the two, but cannot be considered firm.

The results of the study by R. F. Register of du Pont should be noted here (reference 3). He found a direct relationship between water permeation of the laminate at various temperatures and the laminate's retention of flexural strength. The decrease in flexural strength depended upon the amount of water passing through the laminate, and was independent of the time of exposure.

b. Effect of Curing Agent Concentration on Specific Permeability

Curing agent variations apparently can have a significant effect on specific permeability (Figure 2). The effects were different, however, for the two systems used. The A cured specimens showed a continuing upward trend in moisture transmission as the amount of curing agent was increased. The MDA cured specimens, on the other hand, showed a maximum at the 100 percent level. This corresponds to the stoichiometric amount of curing agent and resin.

The A curing agent was an aliphatic polyamine used in a concentration of 6 Phr. The MDA curing agent, however, is used in a concentration of 30 Phr. It can be seen, therefore, that although the percent variations in amounts of curing agent were much higher with the A cured system, the actual amount of variation was nearly the same in both cases.

From the limited amount of data available, the only conclusion that can be drawn is that specific permeability can be affected by curing agent concentration.

c. Effect of Fillers and Barrier Materials on Specific Permeability

Table III shows that inorganic fillers in small quantities have very little effect on the specific permeability of the resin. Fiberglass cloth reinforcement appeared to reduce specific permeability somewhat, but this result was probably colored by a reduction in the effective exposure area of the specimen. Paper reinforcement increased the specific permeability considerably.

The metallic coatings were partially effective in reducing specific permeability. Very thin plates, such as the vapor-deposited metal and the flash coats were only marginally effective. The thicker coats, up to a mil thickness, reduced the specific permeability to very low levels. However, moisture transmission was not completely stopped in any specimens.

d. Effect of Sample Thickness on Specific Permeability

Figure III indicates that variations in specimen thickness have only minor effects on specific permeability. There was a small increase in specific permeability with increasing thickness in both systems, however. It should be noted that although thickness does not severely affect specific permeability, it does affect, in inverse ratio, water vapor transmission rates.

e. Effect of Post Cure on Specific Permeability

The effect of post cure on specific permeability apparently depends upon the particular system (Figures 4 and 5). There was a small decrease in specific permeability with the MDA cured system during extended post cure. There was a significant increase, however, with the A cured system and the anhydride cured systems. The significance of these differences is unknown.

4. CONCLUSIONS:

a. The type of curing agent significantly affects the specific permeability of epoxy resin systems.

b. The anhydride systems were relatively high in specific permeability and the aromatic polyamines were low. The aliphatic polyamines and polyamides varied from high to low.

c. Higher temperatures increased specific permeability drastically.

d. The data indicates a possible relationship between the moisture degradation of composites and the specific permeability of the resins.

e. Small amounts of filler materials do not significantly reduce specific permeability of the resin system.

f. Glass reinforcement does appear to reduce specific permeability, probably by decreasing the effective exposure area.

g. Metallic coatings can reduce specific permeability to near zero, depending upon type and thickness.

h. Specimen thickness has only minor effects on specific permeability.

i. Post cure and curing agent concentration can significantly affect specific permeability.

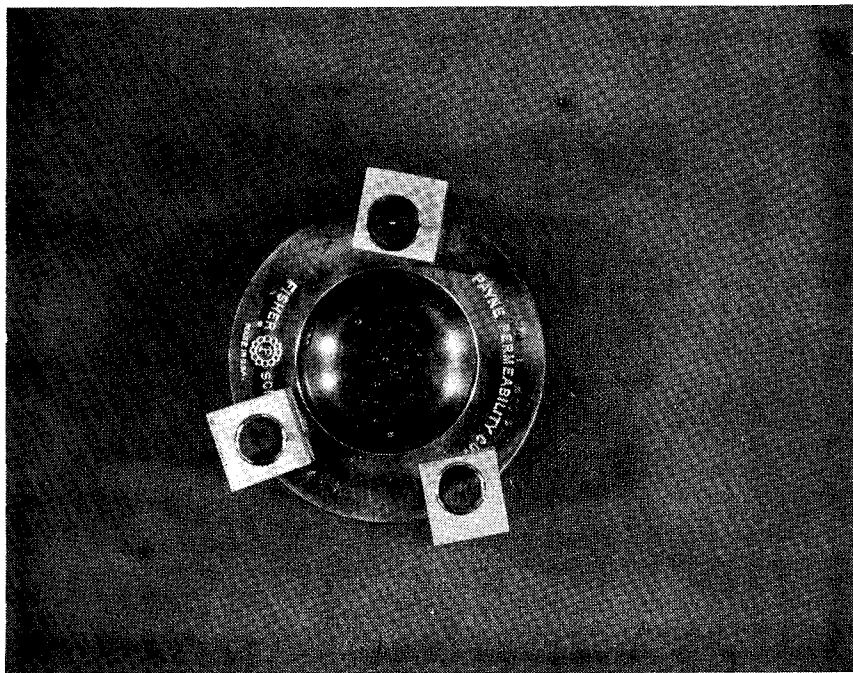


Figure 1. Payne permeability cup.

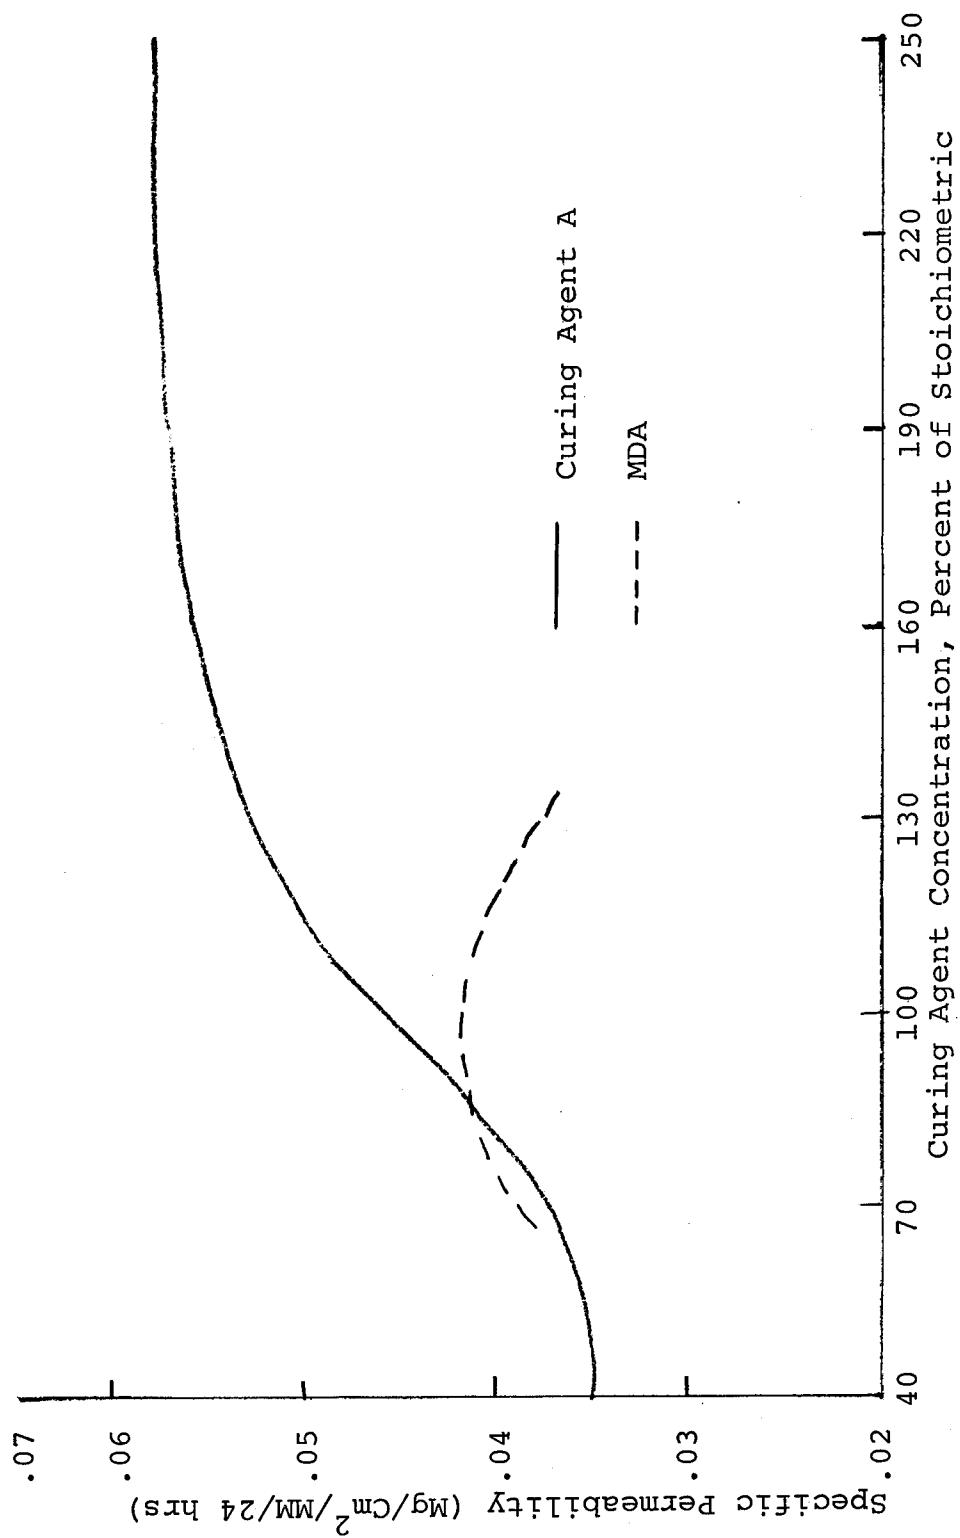


Figure 2. Specific Permeability Versus Curing Agent Concentration



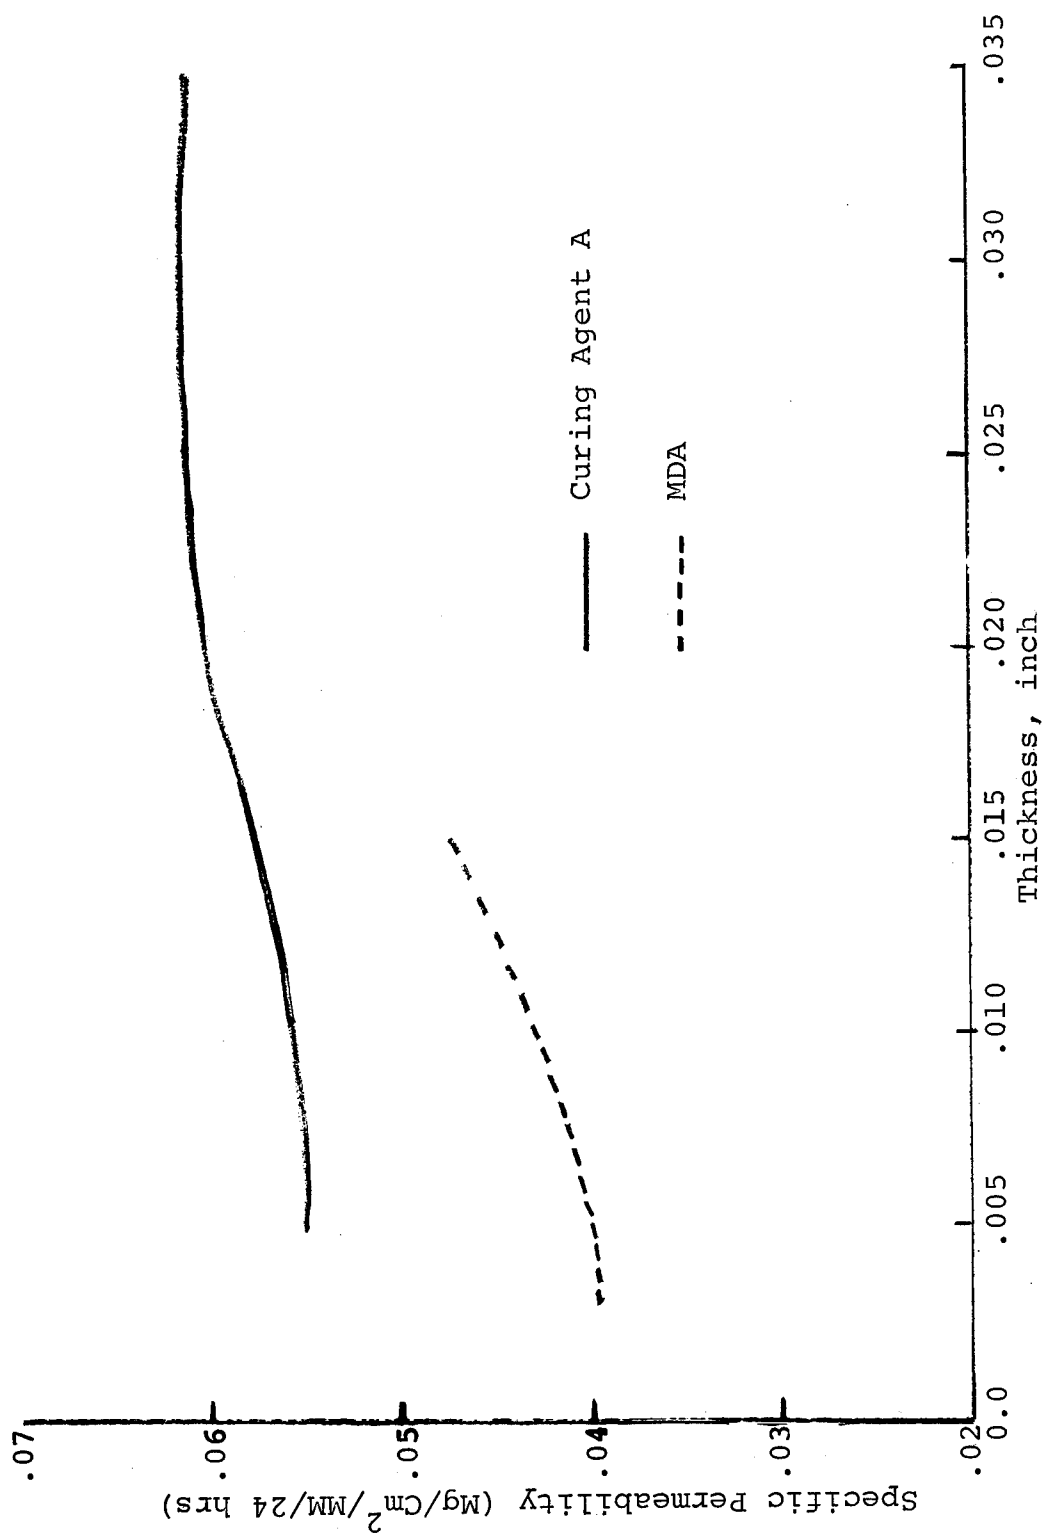


Figure 3. Specific Permeability Versus Thickness

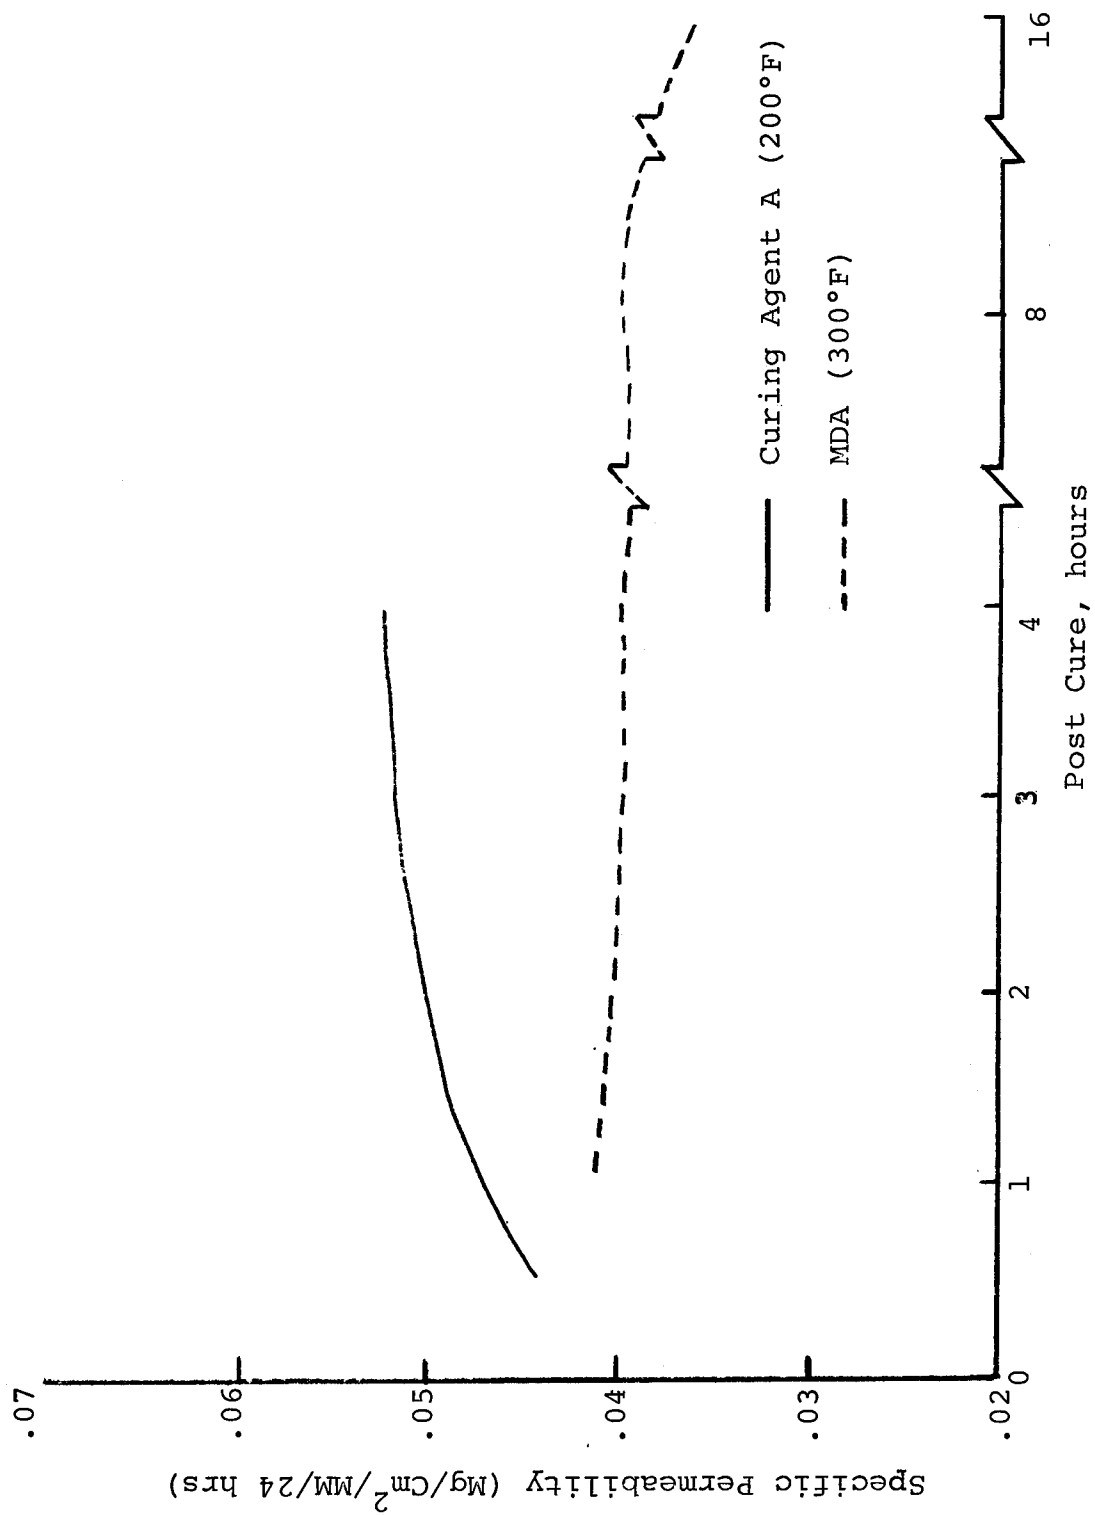


Figure 4. Specific Permeability Versus Post Cure

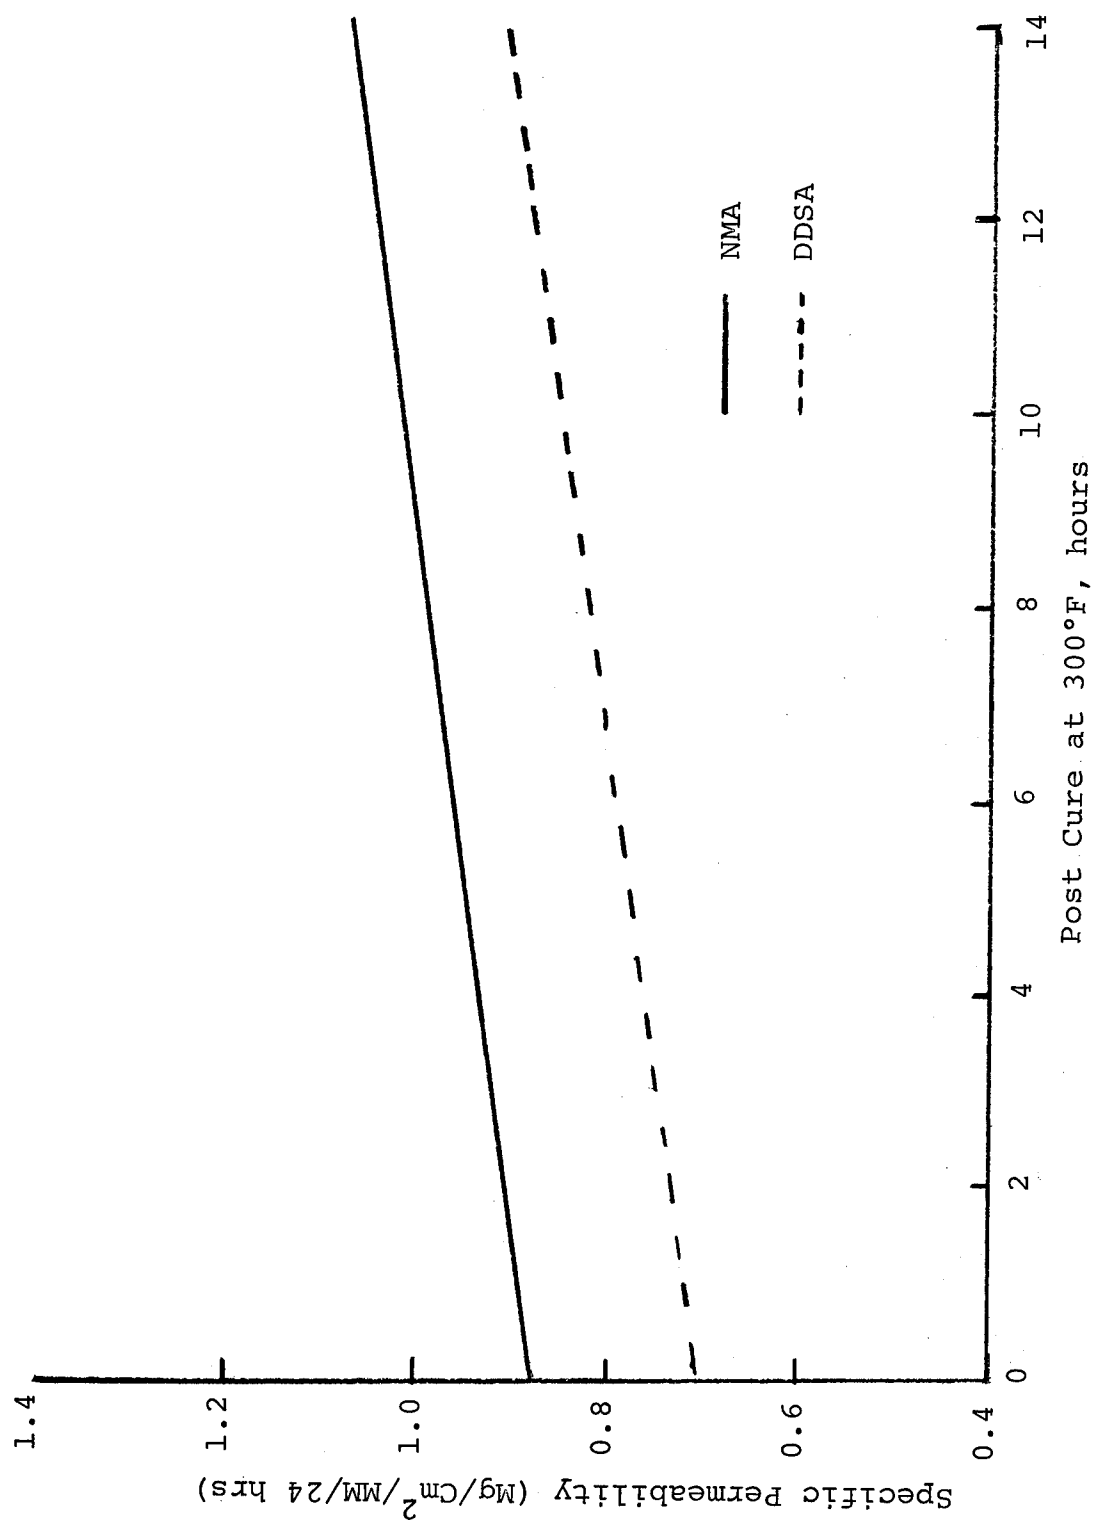


Figure 5. Specific Permeability Versus Post Cure

TABLE I

Data on Curing Agents Used in the Tests

<u>Curing Agents</u>	<u>Type</u>	<u>(PHR) Concentration</u>	<u>Cure Schedule</u>
MDA	Aromatic Polyamine	30	Gel at RT + 2 hrs 300°F
MPDA	Aromatic Polyamine	14	" " "
Z	Aromatic Polyamine	20	" " "
DDS	Aromatic Polyamine	25	" " "
DDSA*	Anhydride	135	2 hrs at 200°F + 2 hrs 300°F
NMA*	Anhydride	90	" " "
V-115	Aliphatic Polyamide	100	RT Gel + 1 hr at 200°F
V-125	Aliphatic Polyamide	55	" " "
V-140	Aliphatic Polyamide	33	" " "
A	Aliphatic Polyamine	6	" " "
DETA	Aliphatic Polyamine	10	" " "
DMP-30	Aliphatic Polyamine	6	" " "

\*0.5% benzyldimethylamine added as an accelerator.

TABLE II

Specific Permeability of Various Epoxy Resin Systems

<u>No.</u>	<u>Curing Agent</u>	<u>Specific Permeability (Mg/Cm<sup>2</sup>/MM/24 hrs)</u>	
		<u>75°F</u>	<u>140°F</u>
1	DETA	.030	.36
2	V-12S	.037	.60
3	V-140	.038	.53
4	Z	.040	.46
5	MPDA	.040	.47
6	MDA	.040	.50
7	DDS	.049	--
8	A	.050	.63
9	V-115	.050	.95
10	DMP-30	.055	.63
11	DDSA	.070	1.35
12	NMA	.085	--

TABLE III

Specific Permeability of An Epoxy Resin System\*  
With Various Coatings and Fillers

<u>No.</u>	<u>Coating or Filler</u>	<u>Specific Permeability</u> (Mg/Cm <sup>2</sup> /MM/24 hrs)
1	Fiberglass Cloth	.030
2	Filter Paper	.120
3	Electroless Nickel Flash	.045
4	Electroless Nickel (.0005")	.015
5	Electroless Nickel (.001")	.010
6	Vapor Deposited Aluminum	.025 - .040
7	Electroless Copper Flash	.045
8	Electroless Copper (.001")	.010
9	Electro-Copper (.001")	.015
10	Vapor Deposited Tin	.035
11	Premetallizing Varnish	.060 - .080
12	Electro-Cadmium (.001")	.005 - .025
13	Electro-Brass (.001")	.020
14	Electro-Zinc (.001")	.020 - .035
15	Electro-Tin (.001")	.005 - .035
16	Calcium Carbonate (20%)	.045 - .055
17	Z-6040 Coupling Agent (3%)	.060 - .070
18	Kaolin (2%)	.050
19	Cabosil (3%)	.050
20	Carbon Black (20%)	.045 - .060
21	Control	.050

\*Epoxy resin plus 6 Phr curing agent A.

#### REFERENCES

1. J. Lynn Parham and E. A. Verchot, "Environmental Compatibility of Glass Reinforced Plastics," Report No. RS-TR-67-6, Army Missile Command, Redstone Arsenal, Alabama.
2. James L. Parham, "Environmental Compatibility of Glass Reinforced Plastics," Report No. RS-TR-70-8, Army Missile Command, Redstone Arsenal, Alabama.
3. R. F. Register, "Behavior of Fiber Reinforced Plastic Materials in Chemical Service," Corrosion, volume 25, number 4, pg 157, April 1969.

# DISTRIBUTION

	No. of Copies
Defense Documentation Center Cameron Station Alexandria, Virginia 22314	20
Office of the Director of Defense Research and Engineering Attn: Mr. J. Persh Room 3D-1085, The Pentagon Washington, D.C. 20301	1
Defense Metals Information Center Battelle Memorial Institute Columbus, Ohio 43215	1
Commanding Officer, Army Research Office Chief, Research and Development Attn: Physical Sciences Division 3045 Columbia Pike Arlington, Virginia 22204	2
Commanding General U.S. Army Materiel Command Attn: AMCRD-CM, Mr. Kaufman Mr. Rivkin Washington, D.C. 20315	1 1
Commanding General U.S. Army Electronics Command Attn: Mr. M. Tenzer Fort Monmouth, New Jersey 07703	1
Commanding General U.S. Army Weapons Command Attn: Mr. B. Gerke, AMSWE-RDR Mr. G. Reinsmith, AMSWE-RDR Rock Island, Illinois 61201	1 1
Commanding General U.S. Army Tank-Automotive Center Attn: Mr. S. Sobak Detroit, Michigan 48090	1
Commanding General U.S. Army Munitions Command Dover, New Jersey 07801	1



No. of Copies

Commanding Officer  
U.S. Army Coating and Chemical Laboratory 1  
Attn: Mr. H. Ammlung  
Aberdeen Proving Ground, Maryland 21005

Commanding Officer  
U.S. Army Materials & Mechanics Research Center  
Attn: Technical Programs Branch, AMXMR-P 4  
Dr. George Thomas 2  
Watertown, Massachusetts 02172

Commanding Officer, Frankford Arsenal  
Attn: Dr. H. Gisser, SMUFA-1330 1  
Mr. H. Markus, SMUFA-1320 1  
Philadelphia, Pennsylvania 19137

Commanding Officer  
Picatinny Arsenal  
Attn: Mr. J. Matlack, Plastics & Packaging Lab 3  
Dover, New Jersey 07801

Commanding Officer  
Watervliet Arsenal  
Attn: Mr. Tom Davidson 1  
Watervliet, New York 12189

Commanding Officer  
U.S. Army Res & Dev Office, Panama  
Attn: STEDO, P.O. Drawer 942 1  
Fort Clayton, Canal Zone

Director, PLASTEC 1  
Picatinny Arsenal  
Dover, New Jersey 07801

Chief, Naval Air Systems Command  
Department of the Navy  
Attn: Mr. P. M. Goodwin 1  
Washington, D.C. 20390

Department of the Navy  
Office of Naval Research  
Attn: Code 423 1  
Washington, D.C. 20350

Department of the Navy  
Special Projects Office  
Attn: SP 271 1  
Washington, D.C. 20350

No. of Copies

Commander U.S. Naval Ordnance Laboratory Attn: Code WM White Oak, Silver Spring Maryland 20907	1
U.S. Air Force Director of Research and Development Attn: LTC J. B. Shipp, Jr. The Pentagon, Room 4D-313 Washington, D.C. 20330	1
6593 Test Group (Development) Attn: Solid Systems Division, DGSC Edwards Air Force Base, California 93523	1
Headquarters Aeronautical Systems Division Attn: Mr. H. Zoeller, ASRCEE-1-2 Mr. R. F. Klinger, ASRCEM-1 Mfg. & Technology Div., ASRCT Wright-Patterson Air Force Base, Ohio 45433	2 2 2
U.S. Atomic Energy Commission Office of Technical Information Extension P.O. Box 62 Oak Ridge, Tennessee 37830	1
National Aeronautics and Space Administration Attn: Mr. R.V. Rhode Washington, D.C. 20546	1
National Aeronautics and Space Administration Marshall Space Flight Center Attn: Mr. R. Schwinghamer, S&E-ASTN-M Mr. W. A. Wilson, S&E-PT-M Huntsville, Alabama 35812	1 1
U.S. Naval Air Engineering Center Aeronautical Materials Laboratory Attn: Mr. Hartley Bowen Philadelphia, Pennsylvania 19112	1
Materials Science Branch Office, Chief of Research and Development Department of the Army Washington, D.C. 20310	1

No. of Copies

Commanding General	
U.S. Army Materiel Command	
Office of Research & Labs, Physical Sciences	
Sciences "A"	
Attn: Mr. Klein	2
Washington, D.C. 20315	
AMCPM-HAE	1
-PE-X	1
-LC	1
-MD	1
-SM-X	1
-TO	1
-MW	1
-LSX	1
-CT	1
-TL	1
-TA	1
-TC	1
AMSMI-XE	1
-XM	1
-QL, Mr. Parr	1
-R, Dr. McDaniel	1
-RF	1
-RB, Dr. Kobler	1
-RN	1
-RC	1
-RR	1
-RK	1
-RE	1
-RG	1
-RD	1
-RL	25
-RT	1
-RBLD	5

UNCLASSIFIED

Security Classification

## DOCUMENT CONTROL DATA - R &amp; D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY (Corporate author) Materials Eng & Dev Function, GE&M Dir Res, Dev, Eng, & Missile Systems Laboratory U.S. Army Missile Command Redstone Arsenal, Ala. 35809		2a. REPORT SECURITY CLASSIFICATION Unclassified	
3. REPORT TITLE SPECIFIC PERMEABILITY OF EPOXY RESIN SYSTEMS		2b. GROUP	
4. DESCRIPTIVE NOTES (Type of report and inclusive dates)			
5. AUTHOR(S) (First name, middle initial, last name) James L. Parham			
6. REPORT DATE 14 June 1971		7a. TOTAL NO. OF PAGES 30	7b. NO. OF REFS 3
8a. CONTRACT OR GRANT NO.		9a. ORIGINATOR'S REPORT NUMBER(S) RL-TR-71-5	
b. PROJECT NO. (DA) 1T062105A329		9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report) AD _____	
c. AMC Management Structure Code No. 502E.11.29500		d.	
10. DISTRIBUTION STATEMENT Distribution of this document is unlimited.			
11. SUPPLEMENTARY NOTES		12. SPONSORING MILITARY ACTIVITY Army Materials & Mechanics Research Center Watertown, Mass. 02172	
13. ABSTRACT Several types of coatings and filler materials were evaluated for their effectiveness in reducing moisture permeability of epoxy resins. Only the metallic coatings gave significant reductions. The specific permeability of a number of epoxy resin systems is given at room temperature and 140°F. Data is presented on the effects of post cure, curing agent concentration, and specimen thickness on specific permeability.			

DD FORM 1473  
NOV 66REPLACES DD FORM 1473, 1 JAN 64, WHICH IS  
OBSOLETE FOR ARMY USE.

UNCLASSIFIED

Security Classification

UNCLASSIFIED

Security Classification

14.	KEY WORDS	LINK A		LINK B		LINK C	
		ROLE	WT	ROLE	WT	ROLE	WT
	Permeability Water Vapor Permeability Epoxy resins Composites Degradation Deterioration						

UNCLASSIFIED

Security Classification